

Abstract

Outdoor statuary in gardens and parks in temperate climates has a tradition of being covered during the winter, to protect against external conditions. There has been little scientific study of the environmental protection that different types of cover provide. This paper examines environmental conditions provided by a range of covers used to protect marble statuary at three sites in the United Kingdom. The protection required depends upon the condition of the marble. Although statues closely wrapped and with a layer of insulation provide good protection, this needs to be considered against the potential physical damage of close-wrapping a fragile deteriorated surface.

Keywords

marble statuary, protective covers, close-wrapping, framed structures, environmental analysis

Assessing the performance of protective winter covers for outdoor marble statuary: pilot investigation

Janet Berry★

Centre for Sustainable Heritage
Bartlett School of Graduate Studies
University College London
Gower Street
London WC1E 6BT
United Kingdom
Fax: (+44) 2079161887
E-mail: janet.berry@ucl.ac.uk
Web site: www.ucl.ac.uk/sustainableheritage

Frances David (formerly English Heritage)

Science Museum
Blythe House
23 Blythe Road
London W14 0QX
United Kingdom

Sophie Julien-Lees

Historic Royal Palaces
Apartment 59
Hampton Court Palace
Surrey KT8 9AU
United Kingdom

Bethan Stanley (formerly National Trust)

English Heritage
37 Tanner Row
York
North Yorkshire
YO31 7TQ
United Kingdom

David Thickett

English Heritage
Room 530
23 Savile Row
London W1S 2ET
United Kingdom

★Author to whom correspondence should be addressed

Introduction

The coverings on outdoor stone statuary aim to provide protection from liquid water, the action of wind, frost, acid pollutants, salt damage, and invasive flora and fauna (Agnew 2001). There are two main approaches to covering statuary. The first is to use framed structures such as wooden boxes (sometimes padded with straw for thermal insulation), metal huts, or tents with heavy-duty tarpaulin or rubberized canvas. The second approach is close-wrapping of the sculpture using a range of waterproof materials, which has included industrial aircraft covers and Tyvek®. With both techniques, water vapour permeable and impermeable covers have been used. There are perceived advantages and disadvantages to both techniques. Usually the choice of cover balances protective requirements with the operational needs of each individual situation. There has been little scientific research into the protective performance, and microclimatic effects under covers. Initial investigative work in the late 1990s suggested that one cover method in particular could possibly create unwanted microclimatic conditions that could adversely affect the statuary.

A project was undertaken with the aim of providing a coherent decision-making framework for the type of cover to use on marble statuary. Marble was chosen as a stone commonly used for outdoor statues and as a material that suffers from degradation outdoors. The project, involving a partnership of English Heritage,

Historic Royal Palaces, the National Trust and University College London, has several objectives. This paper will concentrate on the primary objective of determining the environmental performance of different types of cover.

Deterioration of outdoor marble statuary

Winter covers aim to protect statuary from a range of deterioration mechanisms. However, not all materials react similarly to external factors. Therefore, the first step is to assess critically the most important winter conditions from which marble needs protection.

Liquid water has several effects. Dissolution of calcite in marble by absorbed carbon dioxide in rainwater is an issue, with Haynie (1983) estimating that 75 per cent of marble loss is from this effect. Simon and Snethlage (1996) found a direct correlation between precipitation and surface roughness of exposed marble samples, with losses of up to 25 μm per year in the worst situations. Dissolution of marble is increased by acidic precipitation from gaseous pollutants.

Water also produces wetting and drying cycles of stone. The low porosity of marble and its high tensile strength make it relatively more resistant to the damage from cycles of wetting and drying and the destructive effects of salt crystallization cycles (Torraca 1988). However, marble becomes more susceptible to this form of damage as it ages.

With winter rainfall projected to increase in the UK (Hulme et al. 2002), precipitation will become an increasing factor in the deterioration of outdoor marble statuary.

Another effect of water on marble is freezing. Macro- and microscopic cracks in marble (either present originally in the stone, or formed from other deterioration mechanisms) place marble at risk from frost heave (Torraca 1988). Frost heave occurs in situations where a large pore (such as a hairline crack) is connected to a network of much finer pores. Therefore, porous aged marble is likely to be affected more than less porous newer marble.

A further effect of frost is frost blasting, described by Köhler (1988). Frost blasting again occurs in marbles with greater porosity, but with a low porosity surface layer, which prevents water from migrating out of the stone.

Microbiological organisms cause damage to stone through chemical dissolution and precipitation (Laiz et al. 2002). Their primary impact may be considered minor compared with other factors (Duffy and Perry 1996). However, biological growths are also considered a deleterious aesthetic effect on marble statuary, and their removal through regular cleaning can lead to major surface loss on deteriorated objects.

The extent to which different forms of marble are affected by deterioration mechanisms is influenced by the porosity of the stone. A higher pore volume and larger radii of pores will increase water absorption, thereby increasing surface wetness, leaving the marble more vulnerable to frost damage and biological attack. Rainwashed surfaces will absorb more moisture, increasing the potential for rainwater dissolution over an increased surface area. Furthermore, the increased surface area will increase the potential for chemical dissolution. Therefore, a higher porosity marble in turn makes the marble more susceptible to other deterioration factors.

Therefore protection from rainwater is a major concern for the protection of outdoor statuary during the winter, with freezing an issue for more deteriorated marbles and those with cracks.

Methods

Trials to test the ability of a range of covers to protect statuary from these factors were undertaken during the winter of 2003–04.

Statues and locations

Marble statues at three sites in the UK were chosen. The sites each had a grouping of similar statues suitable for comparative studies. At each site, the

selected statues were of the same stone, of a similar age, had been subjected to similar environmental conditions throughout their life and were located in close proximity to each other. The three sites were chosen to represent different environmental conditions in the UK.

At Anglesey Abbey, in eastern England, a group of early 18th century marble busts, originating in mainland Europe, and now situated in the grounds of the house in a sheltered area since 1953, were selected.

A group of greyhound figures located along the southeasterly aspect of Brodsworth Hall in northern England were carved from Carrara marble in 1850, and were all exposed to high levels of pollution prevalent in the Yorkshire area in the 19th and 20th centuries.

At Hampton Court Palace in southern England, a group of five classical figures were selected, located in an exposed area close to the River Thames. These Carrara marble figures are late 20th century reproductions of 18th century originals.

Different deterioration patterns were evident between the groups, with the busts showing heavy biological growth and friable surfaces, the greyhounds showing biological growth and surface pitting, and the classical figures showing a sound surface with inherent small defects.

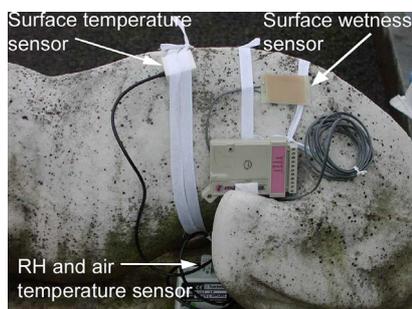


Figure 1. Monitoring equipment installed on marble greyhound, Brodsworth Hall

Monitoring of statues

Monitoring of covered statues was undertaken from December 2003 to April 2004, to capture the cold and wet conditions of a British winter.

For each statue, the same monitoring protocol was observed, namely monitoring surface temperature, air temperature, relative humidity and surface wetness under each of the statue covers (Figure 1). At each site, the same environmental parameters were monitored on an uncovered 'control' statue, for comparable external data. Data were collected using Starlog surface wetness sensors attached to Smartreader 8 ACR loggers, and either Grant Squirrel or Hanwell dataloggers to record surface temperature, air temperature and relative humidity. Surface temperature and wetness sensors were attached to the surface of the statues using cotton tape.

Before and after the monitoring, spot surface wetness readings were undertaken using a Protimeter Aquant inductance meter.

This methodology allowed investigation of the effectiveness of each cover in keeping water out and buffering against external extremes of temperature and relative humidity, in addition to potential problems caused by microclimates under the covers. To determine whether high moisture levels under the covers were a result of liquid water ingress or condensation, time of wetness was monitored, and percentage of time with condensing conditions calculated from temperature and relative humidity data.

The number of frost cycles was recorded through comparing the surface and air temperature under the cover with the uncovered control statue at each site. Increases in biological activity and deterioration of sculpture surfaces were monitored through condition surveys, including photography before and after covering.

Cover methods and materials

The objectives of the trials were:

- to compare the environments created by the two main types of covering technique, namely framed structures and close-wrapping
- to examine the environments created by using water vapour permeable and impermeable materials; and
- to compare the protective properties of a commercially available close-wrapping product and a 'home-made' version.

The types of cover chosen were those that the organizations would typically commission for their sites. At Anglesey Abbey and Brodsworth Hall, where



Figure 2. Covering of marble greyhound, Brodsworth Hall, with P13 polyurethane coated nylon impermeable tent (view of frame with and without cover)



Figure 3. Close-wrapping of marble bust at Anglesey Abbey with the Cliveden Winter Cover (front and back view)

public access is limited in the winter months, experiments were designed to test both framed covers and close-wrapping (Figures 2 and 3). At Hampton Court Palace, which remains open all year round, a variety of close-wrapping methods only were tested (Figure 4). From a presentation viewpoint, close-wrapping reveals the form of the statue and is therefore more acceptable for a visitor. Methods that could be manufactured and erected with relative ease were chosen. The types of material and wrapping regime chosen are displayed in Table 1.



Figure 4. Close-wrapping of marble statues at Hampton Court Palace with (a) water vapour permeable close-wrapping and (b) water vapour permeable close-wrapping with insulation

Results and discussion

Water ingress

Chemical dissolution is a major factor for marble, and hence protection against water should be a main function of a protective cover. The monitoring data demonstrate that the water vapour permeable closewrap with insulation provided

Table 1. Types of cover tested at each site

			Anglesey Abbey	Brodsworth Hall	Hampton Court Palace
Close-wrap	Water vapour permeable covers	P32 polyurethane-coated polyester microfibre	X	X	X
		P32 polyurethane-coated polyester microfibre with under-layer of Quilters Dream Poly [®] polyester wadding Tyvek [®]	X	X	X
	Water vapour permeable interior / impermeable exterior	X	X	X	
Framed structures	Water vapour permeable cover	P32 polyurethane-coated polyester microfibre	X	X	
	Water vapour impermeable cover	PI3 polyurethane coated nylon ²	X	X	
Control		No cover	X	X	X

the best protection against surface wetness. Of all the covers, only the water vapour permeable closewrap at Brodsworth Hall (with and without insulation) provided drier conditions than the uncovered statues (see Table 2). Statues under framed structures and Cliveden Winter Covers were wet for between 78 and 85 per cent of the time at all sites, yet differed in their number of wet–dry cycles. Most covers, to different extents, appeared to inhibit evaporation and retain water on the surface of statues.

Table 2. Results from monitoring data³

Cover Type	Period surface wet (%)	Number of wet/dry cycles	Period condensation possible (%)	RH range (%)	Temperature range (C)	Number of freeze/thaw events	Number of wet and freezing events
Anglesey Abbey (106 days monitoring)							
Control (no cover)	28	122					
Water vapour permeable closewrap	86	18					
Water vapour permeable closewrap with insulation	42	49					
Cliveden Winter Cover			16	53–98	–2 to 14	10	
Water vapour permeable tent	83	38					
Impermeable tent	84	31					
Brodsworth Hall (126 days monitoring ⁴)							
Control (no cover)	44	225	3	29–100	–5.5 to 20.5	34	20
Water vapour permeable closewrap	27	72	16.2	47–100	–4 to 15.5	28	5
Water vapour permeable closewrap with insulation	27	29	12.5	48–100	–3.5 to 14	14	3
Cliveden Winter Cover	85	20	23	90–100	–2.5 to 12	4	4
Water vapour permeable tent	80.5	67	2.4	50–100	–3 to 16.5	17	14
Impermeable tent	80	64	18	37–100	–3 to 17	14	10
Hampton Court Palace (113 days monitoring)							
Control (no cover)				24–100	–3.5 to 18	23	
Water vapour permeable closewrap			20	48–100	–2.5 to 16	15	
Water vapour permeable closewrap with insulation	54	91	19	45–100	–1 to 15.5	11	4
Cliveden Winter Cover	78	17	17	38–100	–1 to 16	11	10
Tyvek [®] closewrap	63	11	20	51–100	–3 to 15	20	11

In general, under most covers, conditions were conducive for condensation for approximately 15–20 per cent of the monitoring period. Under the water vapour permeable tent and closewrap with insulation at Brodsworth Hall, the time for condensation was less. This suggests that breathable properties are important for covering materials, and incorporation of insulation provided a hygroscopic buffer.

All the covers protected against the extremes of RH fluctuations to varying degrees (Figure 5). The absolute humidity under the wraps with insulation was

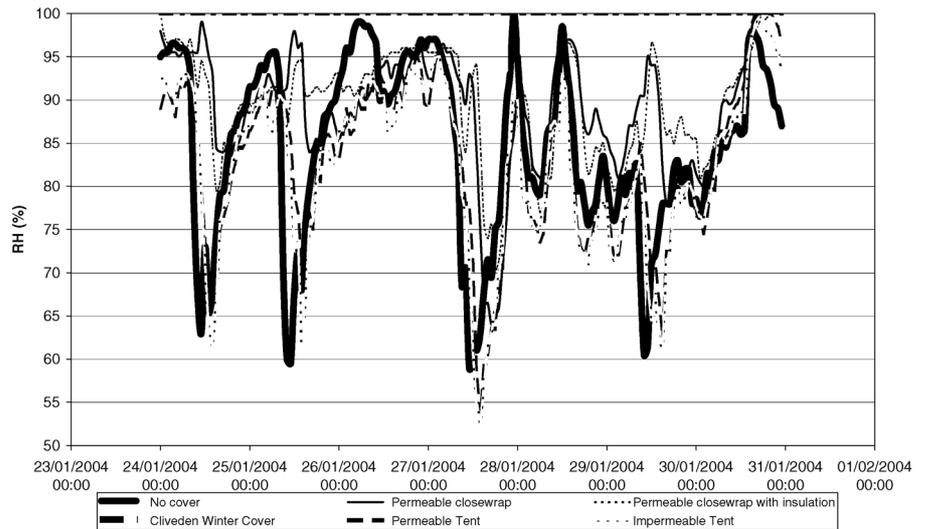


Figure 5. Relative humidity levels under covers, Brodsworth Hall

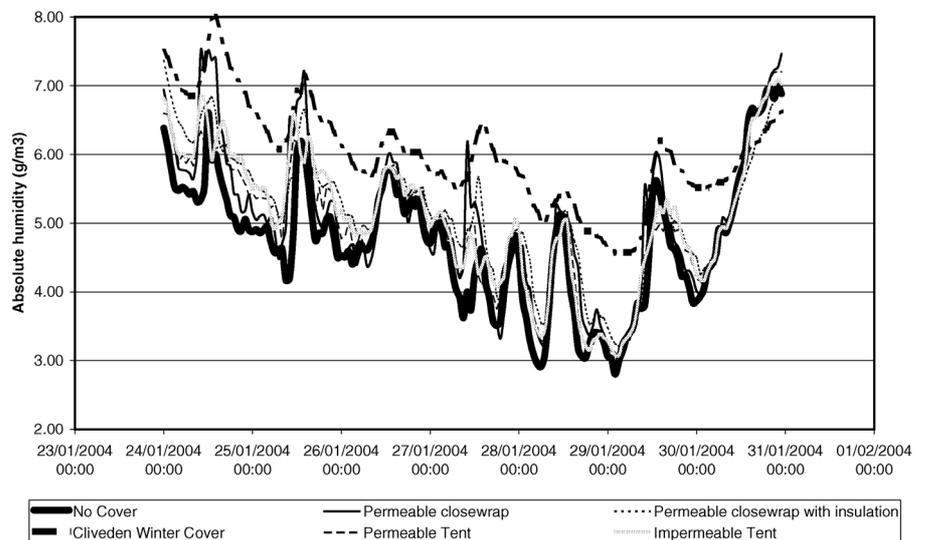


Figure 6. Absolute humidity levels under covers, Brodsworth Hall

generally higher than under the framed structures, and external conditions (Figure 6).

A comparison of the wetness and condensation data suggests that as conditions for condensation existed for 15–20 per cent of the time, while the time of wetness was significantly greater, much of the moisture was water from rain events.

Frost protection

Statue wetness combined with freezing temperatures may lead to freeze–thaw damage of statues. Maintaining temperatures above freezing is an important aspect of the protection covers can provide. At all sites, ambient temperatures fell below 0 °C on several occasions during the winter. Of the covers tested, the Cliveden Winter Cover provided the most effective protection from freezing cycles (Figure 7). This was followed by the water vapour permeable closewrap with insulation. The framed structures provided similar thermal protection and performed better than the water vapour permeable wrap without insulation, and Tyvek[®].

However, analysis of the incidents where statues were simultaneously wet and at temperatures below 0 °C under a cover reveals that the water vapour

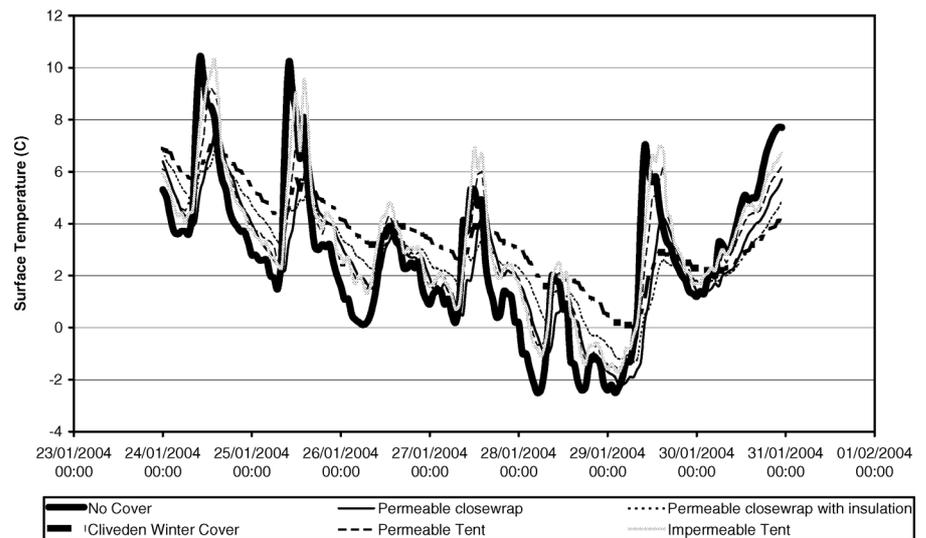


Figure 7. Surface temperature levels under covers, Brodsworth Hall

permeable closewrap with insulation created fewest incidents. In general, the close-wrapped statues were less likely to be wet during periods below 0 °C.

Therefore, the water vapour permeable closewrap with insulation, although not providing as much thermal protection as the Cliveden Winter Cover, provided good freeze–thaw cycle protection as it maintained a drier stone surface during freezing periods.

Biological activity

During the period of monitoring, there was no noticeable difference between the amount of biological activity on the uncovered and covered statues at all sites. However, observations of statues that are regularly covered at Brodsworth Hall indicate that over 5 years, biological growth on covered statues was noticeably lower than on uncovered statues. It will be interesting to observe over time whether the increased dampness under some covers provides a source of moisture that encourages biological agents. Insects and small mammals demonstrated no preference for framed or close-wrapped statues, living under all covers.

Discussion

Considering the deterioration of marble, the factors for which covers are appropriate depend upon the morphology and deterioration state of the marble. For new marble with very low porosity, freeze–thaw cycles are less of an issue than for damaged marble with higher porosity.

There is discussion as to whether framed structures provide better protection than close-wrapping. One of the arguments for using framed structures is to encourage airflow around the statues, thus minimizing the amount of time that the statue remains wet. Framed structures also do not touch the object, thereby limiting physical damage. In general, the air under the framed structures did provide greater mixing with external air, with absolute humidities similar to external conditions. However, this mixing did not keep the surface of the stone drier than the statues closewrapped with the water vapour permeable covers.

Conclusions

This paper discusses the environmental conditions provided by each of the tested covers. From these data, it can be seen that close-wrapping of statues using a method involving insulation (water vapour permeable cover with insulation or Cliveden Winter Cover) appeared to provide good protection from freeze–thaw cycles, and stable humidity levels, albeit generally higher than external absolute humidity levels. Framed structures provided better frost protection than for

statues with no covers at all. Of concern for most covers tested was the increase in wetness under the covers as opposed to uncovered statues. However, all covers protect from the washing of surfaces from rain.

During the winter of 2004, monitoring will be repeated to verify the results. Future trials will analyse the composition of the water on the surface of statues at the end of the winter, to determine the amount of chemical dissolution that has occurred.

When covering statues, environmental conditions are just one of many factors that need to be taken into consideration. Close-wrapping involves close physical contact with the stone surface, where care is needed if the surface is friable. The aesthetic appearance of the covers, their initial and maintenance costs, and summer storage also need to be considered.

A risk matrix is being developed, to enable the environmental data to be placed within the context of the wider decision-making process. This matrix will form the basis of guidance notes for sites within the organizations taking part in this project.

Acknowledgements

We thank the following for their physical and intellectual input into the project: house and garden staff at Anglesey Abbey, Brodsworth Hall and Hampton Court Palace; Suzanne Groom, Phoebe Mason, Linda Bullock, May Cassar, Nigel Blades, Kathryn Hallett, Cliveden Conservation Workshop, University of Leicester, and the Science Museum, London.

Notes

- 1 The Cliveden Winter Cover is a cover comprising three layers (a permeable inner layer, a thermal lining and an impermeable outer layer). The cover is made to order, to ensure a close fit to the statue.
- 2 The impermeable tents were constructed with vents, as this is a common approach to enhance ventilation.
- 3 Blank spaces in Table 2 indicate data not available owing to equipment failure.
- 4 Monitoring period for the Cliveden Winter Cover was 99 days.

References

- Agnew, N, 2001, 'Methodology, conservation criteria and performance evaluation for archaeological site shelters', *Conservation and Management of Archaeological Sites*, volume 5.
- Duffy, A P and Perry, S H, 1996, 'The mechanisms and causes of Portland limestone decay – a case study' in Riederer, J (ed.), *Preprints of the 8th international Congress on Deterioration and Conservation of Stone*, Berlin, Druck, 135–145.
- Haynie, F A, 1983, 'Deterioration of marble', *Durability of Building Materials* 1 (3), 241–254.
- Hulme, M, Jenkins, G J, Lu, X, Turnpenny, J R, Mitchell, T D, Jones, R G, Lowe, J, Murphy, J M, Hassell, D, Boorman, P, McDonald, R and Hill, S, 2002, 'Climate change scenarios for the United Kingdom: the UKCIP02 scientific report', Tyndall Centre for Climate Change Research, School of Environmental Sciences, University of East Anglia, Norwich, UK, http://www.ukcip.org.uk/scenarios/sci_report/sci_report.html.
- Köhler, W, 1988, 'Preservation problems of Carrara marble sculptures Potsdam-Sanssouci ("Radical structural destruction" of Carrara marble)' in Ciabach, J (ed.), *Proceedings of the Vth International Congress on Deterioration and Conservation of Stone*, Torun, Nicholas Copernicus University Press Department, 653–662.
- Laiz, L, Gonzalez, J M and Saiz-Jimenez, C, 2002, 'Microbial communities in caves: ecology, physiology and effects on Palaeolithic paintings', www2.bio.uniroma2.it/lab/algae/Laizetal2002a.htm.
- Simon, S and Snethlage, R, 1996, 'Marble weathering in Europe – results of the Eurocare-Euromarble exposure programme 1992–1994' in Riederer, J (ed.), *Preprints of the 8th international Congress on Deterioration and Conservation of Stone*, Berlin, Druck, 159–166.
- Torraca, G, 1988, *Porous Building Materials: Materials Science for Architectural Conservation*, third edition, Rome, ICCROM.

Materials

Grant Squirrel datalogger
Grant Instruments
(Cambridge) Ltd
29 Station Road
Shepreth
Cambridgeshire SG8 6GB
United Kingdom

Hanwell 3-channel datalogger
Hanwell Instruments Limited
12-13 Mead Business Centre
Mead Lane
Hertford SG13 7BJ
United Kingdom

Starlog surface moisture detector
Unidata
Unit 2
Turner Business Park
Sheffield S13 8HT
United Kingdom

Smartreader 8 ACR loggers

Protimeter Aquant inductance meter
Protimeter PLC
Meter House
Fieldhouse Lane
Marlow
Buckinghamshire SL7 1LW
United Kingdom

P13 waterproof heavy polyurethane coated nylon and P32 polyurethane-coated polyester microfibre
Pennine Outdoor
2 Station Road
High Bentham
North Yorkshire LA2 7LF
United Kingdom

Quilters Dream Poly[®] polyester wadding
The Cotton Patch
1285 Stratford Road
Hall Green
Birmingham B28 9AJ
United Kingdom

Cliveden Winter Cover
Cliveden Conservation Workshop Limited
The Tennis Courts
Cliveden Estate
Taplow
Berkshire SL6 0JA
United Kingdom

Tyvek[®]
Preservation Equipment Ltd
Vinces Road
Diss
Norfolk IP22 4HQ
United Kingdom

Frames for Brodsworth Hall
Sheerspeed Shelters Ltd
4 Kingsgate
Duchy Road
Honiton
EX14 1YD
United Kingdom